

No. CRSSA/09144/18

Date: 06/07/2018

Page: 1 of 7

CRS Ref. CRSSA/18/1702/CSC

CSC STEEL SDN BHD 180, KAWASAN INDUSTRI AYER KEROH, AYER KEROH 75450 MELAKA, MALAYSIA

The following merchandise was (were) submitted and identified by the client as:

Sample Description : realzinc™ Enhance

Sample Receiving Date : 02/07/2018

Testing Period : 02/07/2018 to 06/07/2018

Test Requested : Selected test(s) as requested by client

Test Method : Please refer to next page(s).

Test Results : Please refer to next page(s).

Analysts : Tan Mei Ann & Ling Yii Ming

SGS (MALAYSIA) SDN. BHD.

TAY SIAM PINE B.Sc.(HONS) MMIC TECHNICAL MANAGER



**Test Report** No. CRSSA/09144/18 Date: 06/07/2018 Page: 2 of 7

CRS Ref. CRSSA/18/1702/CSC

Test results:

Test Part Description:

Sample Description : realzinc™ Enhance

## RoHS Directive 2011/65/EU Annex II

Test Item(s):	Unit	Test Method	Results	MDL	Limit
Cadmium (Cd)	mg/kg	With reference to IEC 62321-5:2013 (Determination of Cd by ICP-OES)	N.D.	2	100
Lead (Pb)	mg/kg	With reference to IEC 62321-5:2013 (Determination of Pb by ICP-OES)	N.D.	2	1000
Mercury (Hg)	mg/kg	With reference to IEC 62321-4:2013/AMD 1:2017 (Determination of Hg by ICP-OES)	N.D.	2	1000
Hexavalent Chromium (CrVI) #	μg/cm <sup>2</sup>	With reference to IEC 62321-7-1:2015 (Determination of CrVI by UV-VIS)	N.D.	0.10	-
Sum of PBBs	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBB by GC-MS)	N.D.	-	1000
Monobromobiphenyl	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBB by GC-MS)	N.D.	5	-
Dibromobiphenyl	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBB by GC-MS)	N.D.	5	-
Tribromobiphenyl	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBB by GC-MS)	N.D.	5	-
Tetrabromobiphenyl	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBB by GC-MS)	N.D.	5	-
Pentabromobiphenyl	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBB by GC-MS)	N.D.	5	-
Hexabromobiphenyl	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBB by GC-MS)	N.D.	5	-
Heptabromobiphenyl	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBB by GC-MS)	N.D.	5	-
Octabromobiphenyl	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBB by GC-MS)	N.D.	5	-
Nonabromobiphenyl	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBB by GC-MS)	N.D.	5	-
Decabromobiphenyl	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBB by GC-MS)	N.D.	5	-

SGS (MALAYSIA) SDN. BHD.

TAY SIAM PINE B.Sc.(HONS) MMIC TECHNICAL MANAGER



No. CRSSA/09144/18

Date: 06/07/2018

Page: 3 of 7

CRS Ref. CRSSA/18/1702/CSC

Sum of PBDEs	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBDE by GC-MS)	N.D.	-	1000
Monobromodiphenyl ether	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBDE by GC-MS)	N.D.	5	-
Dibromodiphenyl ether	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBDE by GC-MS)	N.D.	5	-
Tribromodiphenyl ether	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBDE by GC-MS)	N.D.	5	-
Tetrabromodiphenyl ether	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBDE by GC-MS)	N.D.	5	-
Pentabromodiphenyl ether	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBDE by GC-MS)	N.D.	5	-
Hexabromodiphenyl ether	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBDE by GC-MS)	N.D.	5	-
Heptabromodiphenyl ether	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBDE by GC-MS)	N.D.	5	-
Octabromodiphenyl ether	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBDE by GC-MS)	N.D.	5	-
Nonabromodiphenyl ether	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBDE by GC-MS)	N.D.	5	-
Decabromodiphenyl ether	mg/kg	With reference to IEC 62321-6:2015 (Determination of PBDE by GC-MS)	N.D.	5	-

#### Note:

- (a) mg/kg = ppm; 0.1wt% = 1000ppm
- (b) N.D.= Not Detected
- (c) MDL = Method Detection Limit
- (d) # = a. The sample is positive for CrVI if the CrVI concentration is greater than 0.13 μg/cm<sup>2</sup>. The sample coating is considered to contain CrVI
  - b. The sample is negative for CrVI if CrVI is N.D. (concentration less than 0.10  $\mu g/cm^2$ ). The coating is considered a non-CrVI based coating
  - c. The result between 0.10  $\mu g/cm^2$  and 0.13  $\mu g/cm^2$  is considered to be inconclusive unavoidable coating variations may influence the determination

For corrosion protection coatings on metals: Information on storage conditions and production date of the tested sample is unavailable and thus results of Cr(VI) represent status of the sample at the time of testing.

(e) - = not regulated

SGS (MALAYSIA) SDN. BHD.

TAY SIAM PINE B.Sc.(HONS) MMIC TECHNICAL MANAGER



**Test Report** No. CRSSA/09144/18 Date: 06/07/2018 Page: 4 of 7

CRS Ref. CRSSA/18/1702/CSC

Test result:

**Test Part Description**:

Sample Description : realzinc™ Enhance

#### RoHS Directive 2011/65/EU Annex II (amended by Directive (EU) 2015/863)

Test Item(s):	Unit	Test Method	Results	MDL	Limit
Bis (2-ethylhexyl) phthalate (DEHP) (CAS No. 117-81-7)	mg/kg	With reference to IEC 62321-8:2017. Analysis was performed by GC/MS.	N.D.	50	1000
Butyl benzyl phthalate (BBP) (CAS No. 85-68-7)	mg/kg	With reference to IEC 62321-8:2017. Analysis was performed by GC/MS.	N.D.	50	1000
Dibutyl phthalate (DBP) (CAS No. 84-74-2)	mg/kg	With reference to IEC 62321-8:2017. Analysis was performed by GC/MS.	N.D.	50	1000
Diisobutyl phthalate (DIBP) (CAS No. 84-69-5)	mg/kg	With reference to IEC 62321-8:2017. Analysis was performed by GC/MS.	N.D.	50	1000

Note: (a) mg/kg = ppm; (0.1wt% = 1000ppm)

- (b) N.D. = Not Detected
- (c) MDL = Method Detection Limit
- (d) = Not regulated
- (e) On 4 June 2015, Commission Directive (EU) 2015/863 was published in the Official Journal of the European Union (OJEU) to include the phthalates BBP, DBP, DEHP and DIBP into ANNEX II of the Rohs Recast Directive. The new law restricts each phthalate to no more than 0.1% in each homogeneous material of an electrical product.
- (f)The restriction of DEHP, BBP, DBP and DIBP shall apply to medical devices, including in vitro medical devices, and monitoring and control instruments, including industrial monitoring and control instruments, from 22 July 2021.
- (g)The restriction of DEHP, BBP, DBP and DIBP shall not apply to cables or spare parts for the repair, the reuse, the updating of functionalities or upgrading of capacity of EEE placed on the market before 22 July 2019, and of medical devices, including in vitro medical devices, and monitoring and control instruments, including industrial monitoring and control instruments, placed on the market before 22 July 2021.
- (h)The restriction of DEHP, BBP and DBP shall not apply to toys which are already subject to the restriction of DEHP, BBP and DBP through entry 51 of Annex XVII to Regulation (EC) No 1907/2006.

SGS (MALAYSIA) SDN. BHD.

TAY SIAM PINE B.Sc.(HONS) MMIC TECHNICAL MANAGER



No. CRSSA/09144/18

CRS Ref. CRSSA/18/1702/CSC

Date: 06/07/2018


Page: 5 of 7

**Test Part Description**:

Sample Description

realzinc™ Enhance

#### CSC STEEL SDN BHD CRSSA/09144/18

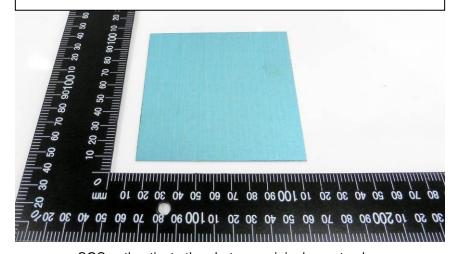

SGS authenticate the photo on original report only

SGS (MALAYSIA) SDN. BHD.

TAY SIAM PINE B.Sc.(HONS) MMIC TECHNICAL MANAGER



No. CRSSA/09144/18

CRS Ref. CRSSA/18/1702/CSC

Date: 06/07/2018

Page: 6 of 7

#### 1. DETERMINATION OF CADMIUM CONTENT BY IEC 62321-5 2013

Sample Receiving and Registration

Cut sample in small pieces

Weight sample (0.2-0.5g) into digestion vessel

Acid digestion (Hotplate)

"Totally Dissolved"

Filtration

Analyses by ICP

#### 2. <u>DETERMINATION OF LEAD CONTENT BY</u> IEC 62321-5 2013

Sample Receiving and Registration

Cut sample in small pieces

Weight sample (0.2-0.5g) into digestion vessel

Acid digestion (Hotplate)

"Totally Dissolved"

Filtration

Analyses by ICP

#### 3. DETERMINATION OF MERCURY CONTENT BY IEC 62321-4 2013/AMD1 2017

Sample Receiving and Registration

Cut sample in small pieces

Weight sample (0.1-0.5g) into digestion vessel

Acid digestion (Hotplate)

"Totally Dissolved"

Filtration

Analyses by ICP

### 4. <u>DETERMINATION OF HEXAVALENT CHROMIUM</u> BY IEC 62321-7-1 2015

Sample Receiving and Registration

Sample Preparation

Boiling-water-extraction

Analyses by UV- Spectrophotometer

Test Report

# 5. DETERMINATION OF PBB/PBDE WITH GC-MS

Analyses by GC-MS (with appropriate dilution)

# BY IEC 62321-6 2015

Cut sample in small pieces

Weight sample (0.5-4.0g) into extraction thimble

Soxhlet Extraction with Toluene

Filter through 0.45 um membrane filter

SGS (MALAYSIA) SDN. BHD.

TAY SIAM PINE B.Sc.(HONS) MMIC **TECHNICAL MANAGER** 




No. CRSSA/09144/18 CRS Ref. CRSSA/18/1702/CSC

Date: 06/07/2018

Page: 7 of 7

### Flowchart for Phthalates Measurement

Method: IEC62321

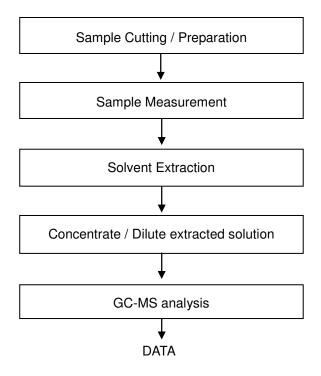

\*\*\*\*End of Report\*\*\*\*

SGS (MALAYSIA) SDN. BHD.

TAY SIAM PINE B.Sc.(HONS) MMIC TECHNICAL MANAGER